

# Physicochemical properties and *in vitro* digestibility of resistant starches obtained by autoclaving and lintnerization from native corn, apple and malanga starches

Propiedades fisicoquímicas y digestibilidad *in vitro* de almidones resistentes obtenidos por autoclaveado y lintnerización a partir de almidones nativos de maíz, manzana y malanga

Viridiana Aguilar-Mendoza<sup>1</sup>, Paul Baruk Zamudio-Flores<sup>1\*</sup>, Francisco Javier Molina-Corral<sup>1</sup>, Guadalupe Isela Olivas-Orozco<sup>1</sup>, Gilber Vela-Gutierrez<sup>2</sup>, Maria Hernandez-Gonzalez<sup>3</sup>, Haydee Yajaira Lopez-De la Peña<sup>3</sup>, Adalberto Ortega-Ortega<sup>4</sup>, Rene Salgado-Delgado<sup>5</sup>, Vicente Espinosa-Solis<sup>6</sup>

<sup>1</sup> Center for Research in Food and Development, A.C. Cuauhtemoc Unit, Food Physiology and Technology from the Temperate Zone. Avenida Rio Conchos s/n, Industrial Park, PO Box 781, C.P. 31570, Cuauhtemoc City, Chihuahua, Mexico.

<sup>2</sup> Laboratory for Research and Development of Functional Products. Faculty of Nutrition and Food Sciences. University of Sciences and Arts of Chiapas, Libramiento Norte Poniente 1150. Col. Lajas Maciel, C.P. 29000, Tuxtla Gutierrez, Chiapas, Mexico.

<sup>3</sup> Autonomous Agrarian University Antonio Narro, Calzada Antonio Narro 1923. C.P. 2315, Buenavista, Saltillo Coahuila, Mexico.

<sup>4</sup> Faculty of Agrotechnological Sciences, Autonomous University of Chihuahua, Extension Cuauhtemoc, Barrio de la presa s/n, Ciudad Cuauhtemoc, Chihuahua, Mexico, C.P. 31510.

<sup>5</sup> Tecnológico Nacional de México/Instituto Tecnológico de Zacatepec, Graduate-Department of Chemical Engineering and Biochemistry, Calzada Tecnológico 27, Zacatepec, Morelos, Mexico, C.P. 62780.

<sup>6</sup> Autonomous University of San Luis Potosí. Academic Coordination of the South Huasteca Region of the UASLP, km 5, highway Tamazunchale-San Martín, C.P. 79960, Tamazunchale, San Luis Potosí, Mexico.

## ABSTRACT

In this research, the effect of the application of successive autoclaving/cooling and lintnerization (acid hydrolysis) cycles in native starches of corn (NCS), apple (NAS), and malanga (NMS) on the formation of resistant starch (RS) was evaluated, and the physicochemical properties and *in vitro* digestibility of the obtained starches were studied. Autoclaved malanga starch (AMS) presented the highest RS content (14 %) compared to all analyzed starches. Enzymatic hydrolysis of native and modified starches indicated that autoclaving/cooling decreased amylolysis ( $\approx 24 - 41$  %), while with the lintnerization treatment, the reduction was lower ( $\approx 3 - 21$  %), both results compared to their native counterparts. Autoclaving and lintnerization treatments reduced the apparent amylose content by  $\approx 5$  %, producing amylose with lower molecular weights ( $\approx 80 - 87$  kDa) for autoclaved starches, and  $\approx 92 - 101$  kDa for lintnerized starches. The luminosity decreased due to the autoclaving treatment and not to the lintnerization process. These results suggest that malanga starch subjected to autoclaving/cooling cycles could be used in baking applications where an increase of the RS content without affecting the sensory color characteristics is desired.

**Keywords:** Conventional and unconventional sources of starch, acid hydrolysis, resistant starch, *in vitro* starch hydrolysis.

## RESUMEN

En esta investigación se evaluó el efecto de la aplicación de ciclos sucesivos de autoclaveado/enfriamiento y lint-

nerización (hidrólisis ácida) en almidones nativos de maíz (NCS), manzana (NAS) y malanga (NMS) sobre la formación de almidón resistente (AR) y se estudiaron las propiedades fisicoquímicas y digestibilidad *in vitro* de los almidones obtenidos. El almidón de malanga autoclaveado (AMS) presentó el mayor contenido de AR (14 %) en comparación con todos los almidones analizados. La hidrólisis enzimática de los almidones nativos y modificados indicó que el tratamiento de autoclave/enfriamiento disminuyó la amilólisis ( $\approx 24 - 41$  %); mientras que con el tratamiento de lintnerización, la reducción fue menor ( $\approx 3 - 21$  %), ambos resultados comparados con sus contrapartes nativas. Los tratamientos por autoclaveado y lintnerización redujeron el contenido de amilosa aparente en  $\approx 5$  %, produciendo amilosas con menores pesos moleculares ( $\approx 80 - 87$  kDa) para los almidones autoclaveados, y  $\approx 92 - 101$  kDa para los almidones lintnerizados. La luminosidad disminuyó por el tratamiento en autoclave y no por el proceso de lintnerización. Estos resultados sugieren que el almidón de malanga sometido a ciclos de autoclaveado/enfriamiento podría aprovecharse en aplicaciones de panificación donde se desea aumentar el contenido de AR sin afectar las características sensoriales de color.

**Palabras clave:** Fuentes convencionales y no convencionales de almidón, hidrólisis ácida, almidón resistente, hidrólisis de almidón *in vitro*.

## INTRODUCTION

Starch is considered the main polysaccharide reserve in vegetables and constitutes the most abundant carbohydrate

in human nutrition, because it plays an important role in supplying metabolic energy (Obadi *et al.*, 2020). Due to its intestinal digestibility, starch is classified into three fractions: rapidly digestible (RDS), slowly digestible (SDS), and resistant starch (RS), which are digested *in vitro* within the first 20 min, and from 20 to 120 min, or not digested at all, respectively (Ratnaningsih *et al.*, 2019). In the scientific literature, it has been reported that through a variety of physical treatments (heat-moisture treatment, autoclaving, and cooking/cooling cycles), chemical treatments (acid hydrolysis or lintnerization, phosphorylation, acetylation, oxidation, and carboxymethylation) and by enzymatic methods (using  $\beta$ -amylase, isoamylase, pullulanase enzymes), it is feasible to increase the starch RS content from different botanical sources (Chiu and Solarek, 2009). For its study, RS can be classified into five types: RS1 is the one that is physically inaccessible inside the plant tissue, trapped in a protein or cellulose matrix; RS2 is the native starch in the granules, resistant due to its semi-crystalline character; RS3 is considered as retrograde starch, and is produced by physical treatments like heat-moisture and temperature cooling cycles; RS4, is obtained by the chemical modification of native starch; and RS5 which is an amylose-lipid complex, assuming that the aliphatic part of the lipid is included within the amylose helix (Ma and Boye, 2018). The nutritional and physiological importance of RS relies on the fact that it is considered a functional ingredient. It can prevent cardiovascular diseases, colon cancer, type 1 and 2 diabetes, obesity, osteoporosis, hypertension, improve intestinal health, micronutrient absorption, lipid profile, satiety, and the development of probiotic microorganisms (Fuentes-Zaragoza *et al.*, 2010; Ashwar *et al.*, 2016c).

In addition, RS3 can be obtained by autoclaving-cooling cycles of native starch, a simple, safe, and economical physical method (Ratnaningsih *et al.*, 2019). The RS4 resistance is achieved by starch chemical modifications such as lintnerization, esterification, etherification, and crosslinking (Ashwar *et al.*, 2016a). Raungrusmee and Anal (2019) reported a 64% increase in rice starch RS content by autoclaving and lintnerization. Concerning this, in the scientific literature, there are reports on obtaining and characterizing RS from native starch of the main conventional sources of tubers and cereals, such as potato (Kwon *et al.*, 2019), cassava (Abioye *et al.*, 2017), rice (Raungrusmee and Anal, 2019), wheat (Punia *et al.*, 2019) and corn (Li *et al.*, 2020), being the latter the most widely cultivated cereal in the world and the main conventional source of starch (Bustillos-Rodríguez *et al.*, 2019).

Within the feasible non-conventional sources, apple (*Malus domestica* B.) is one of the most consumed fruits worldwide; this fruit, in an immature physiological state and its waste (the part that is not industrialized) is rich in carbohydrates, mainly starch (Kringel *et al.*, 2020). Although the native starch obtained from apples has been characterized (Stevenson *et al.*, 2006; Tirado-Gallegos *et al.*, 2016), to our knowledge there are no reports on obtaining RS from native apple starch. On the other hand, white malanga (*Xanthosoma sagittifolium*) and yellow malanga or taro (*Colocasia*

*esculenta*), are perennial herbaceous plants widely cultivated in tropical regions, which form corms rich in starch. Although native and modified starches have been obtained from both *Xanthosoma sagittifolium* (Ojinnaka *et al.*, 2009) and *Colocasia esculenta* (Deka and Sit, 2016), reports on obtaining RS from these species are insufficient. Simsek and El (2012) produced 35 % RS3 by autoclaving native starch from *Colocasia esculenta*. Espinosa-Solis *et al.* (2021) recently reported the feasibility of obtaining RS3 from malanga flour using the autoclave hydrothermal treatment and performing the RS characterization. Thus, this study aimed to assess the effect of the application of successive cycles of autoclaving/cooling and lintnerization (acid hydrolysis) on the formation of RS3 and RS4, respectively, from native corn, apple, and malanga starches and in evaluating its physicochemical properties and their *in vitro* digestibility. The information obtained could suggest the potential of these resistant starches in food applications, with possible benefits for human health.

## MATERIALS AND METHODS

### Materials

Commercial corn starch (Maizena™, Unilever, Mexico) was acquired at a local market (Cuauhtemoc City, Chihuahua, Mexico). Apples of the Golden Delicious Smoothie variety were used. These fruits were obtained 70 days after full flowering (DAFF) and provided by a commercial orchard in Cuauhtemoc City (Chihuahua State, Mexico). Flour from malanga corms (*Xanthosoma sagittifolium*) obtained from plants grown in the municipality of San Fernando (Chiapas State, Mexico) was used. All chemical reagents used were analytical grade and acquired from Sigma-Aldrich (Toluca, Mexico State).

### Isolation of native apple starch (NAS)

The native apple starch was obtained within 48 h after harvesting the fruit according to the methodology reported by Tirado-Gallegos *et al.* (2016). For this, apples were washed and cut into small pieces, then soaked in distilled water with 0.16 % potassium metabisulfite and ground in a blender (Osterizer, Blender Classic). The suspension was sieved through a 100 mesh sieve (ASTM) and allowed to stand under refrigeration (4 °C) for 12 h. Then, the supernatant was removed by decantation, and the settled starch layer was re-suspended in distilled water and centrifuged at  $10,500 \times g$  for 15 min. Next, the green surface of the obtained pellet was removed with the help of a spatula. The remaining pellet was homogenized with distilled water for 10 min and allowed to stand for 24 h under refrigeration. Then, the supernatant was decanted and washed again; this process was repeated at least three additional times until the supernatant was clear and free of fiber and pigment traces on the sedimented starch. The starch was collected and dried in an oven with hot air circulation at 40 °C for 24 h. Finally, it was ground and sieved in a 100 mesh (ASTM) with a pore opening of 0.149 mm.

### Isolation of native malanga starch (NMS)

The starch isolation was carried out according to the methodology reported by Dai *et al.* (2015), with modifications. First, 100 g of malanga flour were suspended in 500 mL of distilled water and homogenized for 1 h under constant stirring at 300 rpm. The dispersion was sieved through organza cloth; the permeate was centrifuged (Allegra 64R) at  $10,000 \times g$  for 10 min. The supernatant was discarded, and the pellets re-suspended in 1,000 mL of distilled water and kept under stirring for 30 min; this dispersion was sieved through a 250 mesh sieve. The sieve was mixed with 500 mL NaOH 0.05 M and kept under stirring at 300 rpm for 60 min, then centrifuged (10 min at  $10,500 \times g$ ). The supernatant was removed, and the brown layer (pigments, fibers, and proteins) on the pellet's surface was scraped off with the help of a spatula. Subsequently, the starch was washed for 30 min with 0.1 M HCl for neutralization; the dispersion was centrifuged again at  $10,500 \times g$  for 10 min. The supernatant was discarded, and to remove traces of NaCl, the sedimented starch was washed with distilled water (30 min, 300 rpm) and centrifuged (10 min at  $10,500 \times g$ ). The supernatant was decanted, and the starch dried in a forced air oven at 40 °C, ground in a mortar, and sieved through a 100 mesh (ASTM) to standardize the particle size.

### Production of RS3 by autoclaving

The production of resistant starch type III (RS3) was done by physical modification of native starch by autoclaving, according to Berry (1986). First, 100 g of native starch were mixed with 350 mL of distilled water and stirred for 15 min (IKA, RW 20 digital). Next, the starch dispersion was heated in an autoclave (121 - 127 °C) for 1 h, allowed to cool, and stored at 4 °C for 24 h. This process was repeated three times. Subsequently, the starch was subjected to a freeze-drying process (LABCONCO) for 72 h and later ground in a mill (IKA M 20 S3). This procedure was applied for NAS to obtain lintnerized apple starch (LAS); also, for NMS to obtain lintnerized malanga starch (LMS) and to NCS to obtain lintnerized corn starch (LCS).

### Production of RS4 by lintnerization

The production of resistant starch type IV (RS4) was achieved by chemical modification of native starches with acid hydrolysis, following the methodology of Rivas-González *et al.* (2008). First, 100 g of native starch were mixed with 200 mL of 1 M HCl and stirred for 6 h at 50 rpm and 35 °C. Then, 200 mL of 1 M NaOH (pH 6.0) were added. Next, the starch solids were centrifuged (Allegra 64R) 6 times using 2,000 mL of distilled water. Subsequently, they were dried in an oven at 37 °C for 48 h. This procedure was applied to NAS to obtain autoclaved apple starch (AAS); also, to NMS to obtain autoclaved malanga starch (AMS) and to NCS to obtain autoclaved corn starch (ACS).

### Proximal analysis

The following analyses were performed on native and resistant starches (RS3 and RS4). The official AOAC (2002)

methods of analysis described in the 17<sup>th</sup> Edition (2002), ether extract (954.18, subchapter 4.5.02.), moisture (method 934.01 subchapter 4.1.03), ash (method 942.05 subchapter 4.1.10), proteins (991.20 Subchapter. 33.2.11). Finally, the carbohydrate content was calculated by difference according to the equation 1:

$$\% \text{carbohidratos} = 100 - (\% \text{moisture} + \% \text{lipid} + \% \text{protein} + \% \text{ash}) \quad (1)$$

### Enzymatic determinations of total starch (TS), available starch (AS), resistant starch (RS), retrograde resistant starch (RRS)

#### Total starch (TS)

The TS content of each sample was quantified by means of a determination that estimates the total amount of starch available for enzymatic hydrolysis. This determination was according to Goñi *et al.* (1997). First, 50 mg of starch were dispersed in a 2 M KOH solution for 30 min, to gelatinize all the starch molecules. Subsequently, it was incubated at 60 °C for 45 min (pH 4.75) with an amyloglucosidase enzyme solution (Roché brand, no. 102 857, Roche Diagnostics, IN, USA); after this time, the released glucose was determined using the glucose oxidase/peroxidase assay (GOD/POD) (sera-PAK® Plus, Bayer de Mexico, SA de CV). TS content was calculated as glucose (mg)  $\times$  0.9. Potato starch was used as a reference.

#### Available starch (AS)

This determination was carried out according to Holm *et al.* (1989). First, 20 mL of distilled water were mixed with a 500 mg sample, stirred for 10 min, and then 100  $\mu$ L of Termamyl were added. Next, samples were placed in a boiling bath for 20 min and stirred every 5 min until they completed 20 min; then, samples were cooled to 30 - 40 °C and transferred to a 100 mL volumetric flask. Next, in a glass tube, 1 mL of sodium acetate buffer at pH 4.75, 25  $\mu$ L of amyloglucosidase, and 500  $\mu$ L of sample from the 100 mL volumetric flask were placed and incubated for 30 min at 60 °C, under constant stirring. Finally, the content of the tube was transferred to a 10 mL volumetric flask, and 50  $\mu$ L of the sample was taken to determine the glucose released by enzymatic digestion, using the GOD/POD (glucose/oxidase peroxidase) method, reading the optical densities of the samples at 510 nm in a Spectronic Genesis 5 spectrophotometer (Spectronic Instrument, Inc Rochester, NY, USA).

#### Resistant starch (RS)

The methodology described by Goñi *et al.* (1996) was used to determine the indigestible starch content. One hundred mg of starch were weighed in a centrifuge tube, and 10 mL of KCl-HCl pH 1.5 buffer were added, followed by 200  $\mu$ L of pepsin solution (the pepsin solution prepared in a ratio of 25 mg of pepsin with 250 mL of KCl-HCl buffer per sample). The sample was mixed and left in a water bath at 40 °C for 60 min with constant stirring. Once the time had elapsed, the sample was left to stand at room temperature, and 9 mL of trismaleate buffer at pH 6.9 were added, followed by 40 mg of  $\alpha$ -amylase (290 U/mg, from the Sigma-Aldrich brand, San



Luis, Missouri, USA), mixed and incubated for 16 h in a water bath at 37 °C with constant agitation; subsequently, the sample was centrifuged (Allegra 64R) for 15 min at 3000 × *g* at 4 °C. The supernatant was discarded and washed twice with 10 mL of distilled water, centrifuged again, and the supernatant was discarded. Then, 3 mL of distilled water and 3 mL of 4 M KOH were added, and the mixture was left to stand for 30 min at room temperature with constant stirring, then adding 5.5 mL of 2 M HCl and 3 mL of 0.4 M Na acetate buffer (pH 4.75), and subsequently, 25 mL of amyloglucosidase were immediately added and left for 45 min in a water bath at 60 °C with constant stirring. The sample was centrifuged for 15 min at 3000 × *g* at 4 °C and the supernatant was collected and transferred to a 50 mL volumetric flask. The residue was washed twice with 10 mL of distilled water each time, and the supernatant was combined with that previously obtained. Subsequently, it was adjusted to 50 mL, and 50 mL of sample was taken to determine the glucose released by enzymatic digestion, using the GOD/POD method (glucose/oxidase peroxidase, SERA-PAK® Plus, Bayer de México, S.A. de CV), reading the optical densities of the samples at 510 nm in a Spectronic Genesis 5 spectrophotometer (Spectronic Instrument, Inc Rochester, NY, USA).

#### Retrograde resistant starch (RRS)

The methodology described by Saura-Calixto *et al.* (1993) was used to determine the content of retrograde resistant starch in samples. First, 100 mg of starch were placed in a centrifuge tube, adding 10 mL of 0.08 M phosphate buffer at pH 6.0 and 10 mL of thermostable α-amylase (290 U/mg, Sigma-Aldrich brand, San Luis, Missouri, USA), and incubated in a boiling water bath for 30 min with constant stirring. Subsequently, they were allowed to cool to room temperature, then 2 mL of 0.0275 N NaOH and 100 µL of protease (170 U/mg, Sigma-Aldrich brand, San Luis, Missouri, USA) were added and incubated at 60 °C for 30 min with constant stirring, and allowed to cool to room temperature. Two mL of 0.325 N HCl and 60 µL of amyloglucosidase (15 U/mL, Roche, IN, USA) were added and incubated at 60 °C for 30 min. The sample was centrifuged for 15 min at 3000 × *g* at 4 °C, and the supernatant discarded. The residue was washed with 10 mL of distilled water, 10 mL of 96 % ethyl alcohol, and 10 mL of acetone, then centrifuged, and the supernatant discarded. Three mL of distilled water were added to the residue and dispersed. Subsequently, 3 mL of 4 M KOH were added and kept under stirring for 30 min at room temperature (25 ± 3 °C). Then, 5.5 mL of 2 N HCl, 3 mL of acetate buffer at pH 4.78 and 60 µL of amyloglucosidase (15 U/mL, Roche brand, IN, USA) were added and incubated at 60 °C for 30 min with constant agitation. Then, it was centrifuged at 3000 × *g* for 15 min at 4 °C, the supernatant saved, and the residue re-suspended in 10 mL of distilled water; the centrifugation was repeated 2 more times. Three mL of distilled water and 3 mL of 4 M KOH were added to the residue, and was kept under constant stirring for 30 min at room temperature. Then, 5.5 of 2N HCl, 3 mL of acetate buffer at pH 4.78 and 60 mL of

amyloglucosidase (15 U/mL, Roche, IN, USA) were added, followed by an incubation at 60 °C for 30 min under constant stirring. Subsequently, it was centrifuged at 3000 × *g* for 15 min at 4 °C, the supernatant saved and re-suspended in 10 mL of distilled water. Centrifugation was repeated, and the supernatants were collected and calibrated at 100 mL. Fifty µL were used to determine the glucose content by the GOD/PAD method (glucose/oxidase peroxidase, SERA-PAK® Plus, Bayer de México, S.A. de C.V.), reading the optical densities of the samples at 510 nm in a Spectronic Genesis 5 spectrophotometer (Spectronic Instrument, Inc Rochester, NY, USA).

#### Color evaluation

It was carried out using a Minolta colorimeter (Model CR-300, Osaka, Japan), and the color variables were reported according to the CIELAB system (L, a\*, b\*) in addition to the chroma variables (color saturation) and °hue (hue) according to the methodology reported by Aboubakar *et al.* (2008). The instrument was calibrated using a white reference tile. Measurements were made in a glass cell containing the powdered starch on the light source (this cell was placed on a white base), and values recorded in quintuplicate for each starch.

#### Determination of apparent amylose content

For this determination, the starches were defatted in a Soxhlet with an 85 % methanol solution for 24 h. Subsequently, they were washed with ethanol and recovered by filtration. Iodine affinities of defatted starches were measured using an automatic potentiometer (702 SM Tirino, Metrohm, Herisau, Switzerland). Apparent amylose content was calculated by dividing the iodine affinity of defatted starches by 20 %.

#### Determination of amylose molecular weight

The methodology reported by Torruco-Uco *et al.* (2016) was used to determine the molecular weight of amylose. Pullulan standards of various molar masses ( $1.6 \times 10^6$ ,  $3.8 \times 10^5$ ,  $1.8 \times 10^5$ ,  $1.0 \times 10^5$ ,  $4.8 \times 10^4$  and  $1.2 \times 10^4$  g/mol) were used to obtain a linear calibration. Pullulans were dissolved in HPLC-grade water at 25 °C, kept in the dark (overnight), filtered using a 0.2 µm nylon syringe filter, and injected into the HPSEC-RI system. The amylose solubilization procedure was performed with 50 s of microwave heating. The supernatant solution was filtered through a 5 µm nylon syringe filter. The solution was injected (50 µL) into the HPLC AT 1100 (Agilent Technology, Deutschland GmbH Waldbronn, Germany) with gel permeation chromatography-size exclusion chromatography (HPLC-SEC) PL aquagel-OH mixed, 8 µm column (7.5 mm ID × 300 mm; Agilent Technologies Deutschland GmbH Waldbronn, Germany).

The column and detector were kept at 30 °C. HPLC-grade water was used as diluent, carefully degassed, and filtered through Durapore GV membranes (0.2 µm) before use. A flow rate of 1.0 mL/min was used. Data analysis was performed using Agilent's GPC software (Agilent Technologies Deutschland GmbH Waldbronn, Germany). After filtration, the carbohydrate concentration of the supernatant solution was

measured by the sulfuric acid-phenol colorimetric method. The procedure was performed at least five times for each sample.

### **In vitro digestibility**

The *in vitro* digestibility was determined by the methodology reported by Zamudio-Flores *et al.* (2015) with modifications, which in turn is based on the methods reported by Englyst *et al.* (1992) and Regand *et al.* (2011). The enzyme solution for digestion was prepared as follows: 0.9 g of porcine pancreatin (EC 232.468.9, from pig pancreas, activity 8 × USP/g, Sigma-Aldrich, St. Louis, MO) in 4 mL of distilled water and centrifuged at 1,500 *g* for 10 min.

The supernatant (5.4 mL) was mixed with 0.8 mL of diluted amyloglucosidase [0.64 mL of amyloglucosidase (EC 3.2.1.3, 3300 U/mL, Megazyme) diluted to 0.8 mL of distilled water], and 0.2 mL of distilled water was added. This enzyme solution was prepared for each enzyme digestion. One hundred mg of native starches, RS3, RS4, and control (white bread made with wheat flour) were weighed in 50 mL tubes in triplicate, and 10 glass beads (diameter = 5 mm) were added to each tube. Two mL HCl (0.05 M) and 10 mg pepsin were added to the tubes and incubated (37 °C, 30 min) in a shaking bath. Subsequently, 4 mL of sodium acetate buffer solution (0.5 M, pH = 5.2) were added to each tube; freshly prepared enzyme solution (1 mL) was added at 1 min intervals. The mixtures were incubated at 37 °C in a shaking water bath. Aliquots (100 µL) were taken at intervals of 0, 10, 20, 30, 60, 90, 120 and 180 min and mixed with 50 % ethanol (1 mL). These solutions were centrifuged at 800 × *g* (10 min), and the hydrolyzed glucose content of the supernatant was determined using the glucose oxidase/peroxidase assay (Megazyme). The equation 2 determined the percentage of total starch hydrolysis:

$$\%hydrolysis = \left( \frac{\text{free glucose weight} \times 0.9}{\text{starch weight}} \right) \times 100$$

### **Statistical analysis**

The experiments were carried out using a completely randomized design. A one-way analysis of variance (ANOVA,  $p \leq 0.05$ ) was applied using the statistical program Sigma-Stat, version 2.03 (Fox *et al.*, 1995). The size of the analyzed samples was a minimum of three ( $n > 3$ ), and when significant differences were found, the Tukey test was applied to compare the means (Walpole *et al.*, 1999).

## **RESULTS AND DISCUSSION**

### **Proximal chemical analysis**

The proximal chemical analysis is shown in Table 1. The NMS and NAS, as well as their respective lintnerized starches (LMS and LAS), presented the highest moisture contents with values that ranged from ≈ 13 % (NAS) up to ≈ 16 % (NMS) although no significant differences were observed between them ( $p > 0.05$ ). On the other hand, every starch subjected to the physical processing of autoclaving presented the lowest moisture percentages, in the following descending order: AAS > ACS > AMS; however, no significant differences ( $p > 0.05$ ) were observed among them. In this regard, lower moisture values have been reported in native corn starches (6.5 - 8.5 %) (Bustillos-Rodríguez *et al.*, 2018), native oat starch (10.03 - 10.63 %) (Shah *et al.*, 2016) and native (4.89 %) and lintnerized (7.99 %) plantain starch (Aparicio-Saguilán *et al.*, 2005). Recently, it was reported that the moisture content in powders is an essential factor in flow and other mechanical properties and is highly dependent on the method used for its determination, the degree or level of drying, and the humidity in the surrounding atmosphere (Juarez-Enriquez *et al.*, 2019).

The components (mainly lipids and proteins) can influence the functionality of the starch granule; protein is associated with grain hardness; while lipids can significantly reduce the swelling power of starch (Bustillos-Rodríguez *et al.*, 2018). The native and modified starches of corn, malanga, and apple presented proteins, lipids, and ashes values lower than 1 %, with which these polluting components of the starch would be reduced, indicating that these starches

**Table 1.** Proximal chemical analysis of native, autoclaved, and lintnerized starches from corn, apple, and malanga<sup>®</sup>.

**Tabla 1.** Análisis químico proximal de almidones nativos, autoclaveados y lintnerizados de maíz, manzana y malanga<sup>®</sup>.

Sample	Analysis						
	Moisture (%)	Protein (%)	Lipid (%)	Ash (%)	CHO <sup>1</sup> (%)	Amylose (%)	MW (kDa) <sup>2</sup>
NCS	11.12 ± 0.62 <sup>bc</sup>	0.35 ± 0.02 <sup>b</sup>	0.16 ± 0.03 <sup>abcd</sup>	0.09 ± 0.02 <sup>bcd</sup>	88.29 ± 0.11 <sup>bc</sup>	28.62 ± 0.11 <sup>b</sup>	108.28 ± 0.92 <sup>a</sup>
ACS	8.73 ± 0.46 <sup>cd</sup>	0.30 ± 0.01 <sup>bc</sup>	0.11 ± 0.07 <sup>abcd</sup>	0.07 ± 0.01 <sup>cde</sup>	90.77 ± 0.09 <sup>ab</sup>	23.65 ± 0.10 <sup>f</sup>	86.39 ± 0.08 <sup>g</sup>
LCS	11.45 ± 0.90 <sup>bc</sup>	0.20 ± 0.01 <sup>de</sup>	0.12 ± 0.01 <sup>abcd</sup>	0.03 ± 0.01 <sup>e</sup>	88.20 ± 0.19 <sup>bcd</sup>	23.55 ± 0.14 <sup>f</sup>	100.72 ± 0.12 <sup>b</sup>
NMS	16.46 ± 0.22 <sup>a</sup>	0.42 ± 0.02 <sup>a</sup>	0.27 ± 0.03 <sup>a</sup>	0.14 ± 0.01 <sup>ab</sup>	82.71 ± 0.05 <sup>e</sup>	29.84 ± 0.10 <sup>a</sup>	95.53 ± 0.14 <sup>d</sup>
AMS	6.05 ± 0.72 <sup>d</sup>	0.33 ± 0.01 <sup>b</sup>	0.23 ± 0.03 <sup>ab</sup>	0.15 ± 0.01 <sup>a</sup>	93.24 ± 0.14 <sup>a</sup>	24.82 ± 0.07 <sup>d</sup>	80.44 ± 0.15 <sup>h</sup>
LMS	14.02 ± 1.02 <sup>ab</sup>	0.29 ± 0.02 <sup>bc</sup>	0.10 ± 0.00 <sup>bcd</sup>	0.07 ± 0.00 <sup>cde</sup>	85.52 ± 0.19 <sup>cde</sup>	24.18 ± 0.06 <sup>e</sup>	91.64 ± 0.09 <sup>f</sup>
NAS	13.21 ± 0.63 <sup>ab</sup>	0.26 ± 0.01 <sup>cd</sup>	0.17 ± 0.03 <sup>abc</sup>	0.11 ± 0.01 <sup>abc</sup>	86.26 ± 0.12 <sup>cd</sup>	27.37 ± 0.08 <sup>c</sup>	98.23 ± 0.38 <sup>c</sup>
AAS	9.24 ± 0.53 <sup>cd</sup>	0.19 ± 0.01 <sup>e</sup>	0.00 ± 0.00 <sup>d</sup>	0.06 ± 0.00 <sup>cde</sup>	90.51 ± 0.10 <sup>ab</sup>	22.88 ± 0.03 <sup>g</sup>	81.58 ± 0.09 <sup>h</sup>
LAS	14.77 ± 0.54 <sup>a</sup>	0.18 ± 0.02 <sup>e</sup>	0.07 ± 0.03 <sup>cd</sup>	0.05 ± 0.00 <sup>de</sup>	84.94 ± 0.10 <sup>de</sup>	22.69 ± 0.06 <sup>g</sup>	93.59 ± 0.13 <sup>e</sup>

<sup>a</sup>Mean of at least three repetitions ± standard error. Values with the same letter within columns are not significantly different according to Tukey's test ( $p > 0.05$ ). <sup>1</sup>Total carbohydrates (CHO) were obtained by difference (100 % - % rest of the other components). <sup>2</sup>MW = Molecular weight.

were extracted with high purity (Lawal, 2004). Various investigations have reported similar results in native starches from corn, potato, cassava (Waterschoot *et al.*, 2015), malanga (Deka and Sit, 2016), and rice (Ashwar *et al.*, 2016c; Van Hung *et al.*, 2016).

Table 1 also shows that the lintnerization process decreased proteins, lipids, and ashes content in LMS, with significant differences ( $p < 0.05$ ) with respect to its native counterpart; however, in LCS and LAS, this reduction was only observed in proteins and ashes (being statistically significant,  $p < 0.05$ ). This decrement is attributed to the acid used in the lintnerization process, which solubilized an important portion of these components (Aparicio-Sanguilán *et al.*, 2005). After autoclaving modification of native starches, the protein, lipid, and ash content decreased because the thermal treatment caused proteins denaturation and lipids saponification (Aparicio-Sanguilán *et al.*, 2005). In the AMS, the reduction in protein content was significant ( $p < 0.05$ ) compared to NMS. In addition, the AAS protein and lipid content decreased significantly ( $p < 0.05$ ) compared to their native counterpart. At the same time, in the NCS, NMS, and NAS samples, no significant differences were found ( $p > 0.05$ ) in ash content in relation to ACS, AMS, and AAS, respectively, after undergoing the autoclaving process; this was possibly due to the temperature used in the autoclaving process not being high enough to destroy the minerals present in the starch (Aparicio-Sanguilán *et al.*, 2005). These results are consistent with those reported by Aparicio-Sanguilán *et al.* (2005) in autoclaved plantain starches and by Deka and Sit (2016), who reported a similar behavior in starches modified by heat-moisture treatment from malanga.

In relation to the carbohydrate content, no clear or defined trend was observed. In this sense, the autoclaved samples, in general, presented the highest values, while the samples lintnerization did not cause significant changes ( $p > 0.05$ ) with respect to their native counterparts. This could be due to the fact that the values of these components were obtained by difference, which is related to the value of the other components (moisture, proteins, lipids, and ashes). This has been previously reported by Vargas *et al.* (2016) in acetylated potato starches. Regarding the similarities between the conventional and unconventional sources in this determination, NMS and NAS did not present significant differences ( $p > 0.05$ ) in lipids and ashes content compared to NCS.

#### Apparent amylose content

The amylose contents for the NCS, NMS, and NAS samples were  $\approx 29$ , 30, and 27 %, respectively (Table 1). Some studies have reported lower amylose content in corn (22.5 %) (Jane *et al.*, 1999) and malanga starch (22.7 %) (Lawal, 2004), while a value within the interval of 26 - 29.1 % for apple starch was reported by Stevenson *et al.* (2006). The differences found may be due to the variety, harvesting time, and place of cultivation (Simsek and El, 2012). On the other hand, in the modified starches (autoclaved and lintnerized), the amylose content decreased significantly ( $p < 0.05$ ) due to the selective

elimination of amorphous zones during those modifications. The reduction in amylose content in the autoclaved starches is consistent with that reported in the literature for malanga starch modified by a convection process with a hot air oven, where that decrement was attributed to the union of the amylose chains already present with each other or to the amylopectin molecule (Deka and Sit, 2016). However, Babu *et al.* (2014) reported the opposite of this study in autoclaved banana starch where the amylose content increased after autoclaving, which they attributed to a possible partial debranching of amylopectin by the drastic heating and pressure during autoclaving.

The lintnerization treatment decreased the amylose content by approximately 5 % (due to partial hydrolysis) in the three analyzed starches. The results of this study are consistent with those reported by Lawal (2004) in lintnerized malanga starches and by Wang and Wang (2001) in lintnerized potato, corn, and rice starches, who reported a decrease in amylose content during the acid treatment, relative to native starch. The  $H^+$  ions acted mainly on the amorphous regions within the starch granule, and both amylose and amylopectin were hydrolyzed in the acid presence (Wang and Wang, 2001).

No significant differences were observed between the amylose content of the autoclaved and lintnerized corn and apple starches ( $p > 0.05$ ), contrary to what was observed in the modified malanga starches where the lowest amylose content was presented in the lintnerization treatment. In general, we can say that unconventional-source starches differ from those obtained from conventional sources (corn) in terms of amylose content, both in their native and modified forms. It is important to mention that malanga starches (native, autoclaved, and lintnerized) presented higher percentages of amylose compared to the type of modification. Finally, amylose content has been shown to have a significant correlation with higher resistant starch content or lower digestibility (Li *et al.*, 2019).

#### Determination of molecular weight

Starch is a polymer consisting of a mixture of macromolecules of different chain lengths with a very similar molecular structure, so it is difficult to precisely define their molecular weight (MW) (Cai *et al.*, 2019). The native starches MW was higher than that of the modified samples (Table 1), which indicated that the macromolecules (amylose and amylopectin) were fragmented or hydrolyzed due to degradation by the applied treatments. The autoclaved starches from the three botanical sources showed a significant decrease ( $p < 0.05$ ) in MW, with respect to their native counterparts, and this is because the autoclaved starches present a lower content of amylose compared to the native ones (Zeng *et al.*, 2015). This result is consistent with what was reported in autoclaved starch from lotus seeds and in starch subjected to ultrasonic-autoclaved treatment, where a decrease in MW was observed compared to its native starch and high-amylose corn starch (Zeng *et al.*, 2015). The starches modified by acid hydrolysis



(lintnerization) showed a significant MW decrease ( $p < 0.05$ ) compared to the native ones; this is attributed to the fact that the amylose chains are more susceptible to acid hydrolysis instead of the amylopectin chains (Shi *et al.*, 2016).

In the initial attack that occurs in this modification, most of the amylose chains could have been hydrolyzed into shorter chains, while the amylopectin chains were less susceptible to acid attack (Xia *et al.*, 2017). The findings in this study are similar to those reported in hydrolyzed cassava (tapioca) starch at different reaction times, and those in rice starches modified by reactive extrusion through esterification with octenyl-succinylation and acetylation, and in hydrolyzed corn starches, where they presented a decrease in MW, after the chemical modifications (Cai *et al.*, 2019; Xia *et al.*, 2017; Ozturk *et al.*, 2011). In general, we observed that the MW between the various unconventional botanical sources (as well as their respective modifications), presented significant differences ( $p \leq 0.05$ ) compared to the conventional source (corn), being malanga starches (native, autoclaved, and lintnerized) those that presented lower MW.

### Color evaluation

Table 2 shows the color attributes of native and modified (resistant) corn, apple, and malanga starches. Color is a quality indicator criteria in the industrial and commercial use of starches, where white starches indicate a lower protein and pigment contents and, therefore, higher purity (Jan *et al.*, 2017). Therefore, it should not present any coloration for a greater acceptance of the starch (Radley, 1976). Most of the starches showed lightness values ( $L^*$ ) higher than 90, so it can be considered that they presented high whiteness if it is estimated that a value of  $L^* = 100$ , it is white (Tirado-Gallegos *et al.*, 2016); however, AAS and AMS presented lower  $L^*$  (90.47 and 85.55, respectively) values. This result agrees with what was described by Deka and Sit (2016), where their physically modified starch presented lower luminosity values ( $L^*$ ) according to its native counterpart. In starches subjected to the lintnerization treatment (LCS, LAS, and LMS), the whiteness or luminosity ( $L^*$ ) was similar to the native starches (NCS, NAS, and NMS) due to the use of NaOH to neutralize the lintnerized samples, which had a whitening effect (Ashwar *et*

*al.*, 2017). Regarding the coordinates  $a^*$  (red/green) and  $b^*$  (yellow/blue) values, AMS exhibited the highest ones (1.72 and 4.53, respectively), and AAS at coordinate  $b^*$  (5.21). These results are similar to the values reported by Deka and Sit (2016) and Aboubakar *et al.* (2008) in malanga starches. The color change observed in the autoclaved samples, could be attributed to the Maillard reaction between the starch reducing sugars and the protein amino groups during hydrothermal processing (Shah *et al.*, 2016; Gani *et al.*, 2016). In relation to the hue angle variable ( $^{\circ}\text{hue}$ ); this has a value of  $0^{\circ}$  for red,  $90^{\circ}$  for yellow,  $180^{\circ}$  for green, and  $270^{\circ}$  for blue (Whale and Singh, 2007). The LAS presented the highest value in this variable ( $^{\circ}\text{hue} \approx 281$ ), conferring blue tones, followed by LCS, ACS, and NCS, showing yellow tones; while the lowest values were observed in LMS (41.80), NMS (61.46) and AMS (68.36) starches, presenting red tones. These shades in the starch may be due to the presence of pigments in each botanical source used (Tirado-Gallegos *et al.*, 2016).

In the chroma variable (color saturation or intensity), no trend was observed between native and modified starches. AAS presented the highest chroma value (5.26), which was statistically significant compared to the rest of the analyzed starches, followed by AMS (4.66). In native starches, the chroma value was determined in a range of 1.33 - 3.13; these values are lower than those reported by García-Tejeda *et al.* (2011) in native banana starch (10.95); however, the chroma values evaluated in our study are higher than those obtained by Tirado-Gallegos *et al.* (2016) in apple starch (ranges 0.20 - 1.70). The autoclaved starches presented higher values (2.21 - 5.26) than the lintnerized ones (0.49 - 1.32). García-Tejeda *et al.* (2011) reported a chroma value of 5.75 for oxidized plantain starch, which is higher than those found in this study for starches chemically modified by lintnerization. Some researchers have reported that chroma values close to zero are related to the whiteness of the starch (García-Tejeda *et al.*, 2011; Tirado-Gallegos *et al.*, 2016). This result implies that the lintnerized starches of the present study are of greater whiteness than the autoclaved starches, being favorable for their industrial application since this is representative of quality and purity.

**Table 2.** Color variables of native, autoclaved, and lintnerized corn, from apple, and malanga starches<sup>⊗</sup>.

**Tabla 2.** Variables de color de los almidones nativos, autoclaveados y lintnerizados de maíz, manzana y malanga<sup>⊗</sup>.

Samples	Color variables				
	$L^*$	$a^*$	$b^*$	Chroma	$^{\circ}\text{hue}$
NCS	99.56 ± 0.01 <sup>a</sup>	- 1.39 ± 0.01 <sup>g</sup>	2.81 ± 0.00 <sup>c</sup>	3.13 ± 0.01 <sup>c</sup>	116.32 ± 0.18 <sup>c</sup>
ACS	97.52 ± 0.00 <sup>b</sup>	- 0.81 ± 0.00 <sup>e</sup>	2.06 ± 0.02 <sup>d</sup>	2.21 ± 0.01 <sup>d</sup>	111.40 ± 0.27 <sup>cd</sup>
LCS	99.20 ± 0.01 <sup>a</sup>	- 1.01 ± 0.01 <sup>f</sup>	- 0.49 ± 0.01 <sup>g</sup>	1.32 ± 0.01 <sup>e</sup>	139.44 ± 0.63 <sup>b</sup>
NMS	96.00 ± 0.33 <sup>c</sup>	0.63 ± 0.01 <sup>b</sup>	1.18 ± 0.07 <sup>e</sup>	1.33 ± 0.07 <sup>e</sup>	61.46 ± 1.42 <sup>f</sup>
AMS	85.55 ± 0.13 <sup>f</sup>	1.72 ± 0.03 <sup>a</sup>	4.53 ± 0.32 <sup>b</sup>	4.66 ± 0.13 <sup>b</sup>	68.36 ± 0.21 <sup>f</sup>
LMS	97.43 ± 0.09 <sup>b</sup>	0.39 ± 0.07 <sup>c</sup>	0.36 ± 0.07 <sup>f</sup>	0.53 ± 0.10 <sup>f</sup>	41.80 ± 3.74 <sup>g</sup>
NAS	96.42 ± 0.03 <sup>c</sup>	- 0.81 ± 0.02 <sup>e</sup>	2.37 ± 0.03 <sup>cd</sup>	2.51 ± 0.03 <sup>d</sup>	108.82 ± 0.61 <sup>d</sup>
AAS	90.47 ± 0.09 <sup>e</sup>	0.71 ± 0.00 <sup>b</sup>	5.21 ± 0.06 <sup>a</sup>	5.26 ± 0.06 <sup>a</sup>	82.3 ± 0.11 <sup>e</sup>
LAS	94.43 ± 0.09 <sup>d</sup>	0.09 ± 0.02 <sup>d</sup>	0.49 ± 0.04 <sup>g</sup>	0.49 ± 0.04 <sup>f</sup>	280.72 ± 2.39 <sup>a</sup>

<sup>⊗</sup>Mean of at least five repetitions ± standard error. Values with the same letter within columns are not significantly different according to Tukey's test ( $p > 0.05$ ).

In general, the native and lintnerized malanga and apple starches showed differences in the color variables L\*, a\*, chroma, and °hue with the native starch and the LCS, respectively, except for the b\* coordinate; where a similar value was observed in NAS to that obtained in NCS, and LAS was similar to LCS. Regarding the autoclaved malanga and apple starches, these presented differences in L\*, a\*, b\*, chroma, and °hue with respect to ACS.

### Enzymatic determinations of total starch (TS), available starch (AS), resistant starch (RS) and retrograde resistant starch (RRS)

Table 3 shows the contents (determined as a percentage from enzymatic evaluations) of total starch (TS), available starch (AS), resistant starch (RS), and retrograde resistant starch (RRS) quantified in the native and modified starch samples (lintnerized and autoclaved). The TS is considered a qualitative determination of starch purity since it represents an important criterion in its quality, while AS represents the starch susceptible to enzymatic attack (Tirado-Gallegos *et al.*, 2016). We observed that the lintnerization and autoclaving treatments decreased the TS and AS contents in all the samples analyzed, which was more significant in the corn starch sample ( $\approx 5\%$ ). On the contrary, RS and RRS contents presented an inverse behavior to the quantified values of TS and AS since RS and RRS increased in all the samples when they were subjected to the lintnerization and autoclaving treatments. Interestingly, we observed that the highest RS amount ( $\approx 14\%$ ) was obtained in the malanga starch sample when it was subjected to autoclaving.

Similar results in obtaining RS (by the physical treatment of autoclaving) have been reported in plantain starches, with values that increased from 1.51% (for native starch) to 16.02% (for autoclaved starch) (Aparicio-Saguilán *et al.*, 2005), in corn starches (from 0.68% for native starch to 8.47%) (Neder-Suárez *et al.*, 2018), and wheat starch with values that increased from 0.3% to 4.8% (Berry, 1986). The RS increment can be attributed to the heating and cooling cycles made by the autoclave. Autoclaving is a treatment that combining the gelatinization process (which disrupts the granular structure by heating a starch dispersion in excess water) and the retrogradation process (which produces recrystallization of starch components) upon cooling, resulting in higher production of RS and RRS (Babu *et al.*, 2014). Similarly, in the chemical modification (lintnerization), the RS values are increased due to the depolymerization of the amylose chains and amylopectin branches; however, the lintnerization does not entirely degrade the crystalline structure (Franco *et al.*, 2002), which can produce a starch resistant to enzymatic hydrolysis (Aparicio-Saguilán *et al.*, 2005). These results agree with the values recently reported by Neder-Suárez *et al.* (2018), with values that increased from 0.68% to 2.10% in corn starch subjected to acid hydrolysis and in lintnerized banana starch (from 1.51% to 2.61%) (Aparicio-Saguilán *et al.*, 2005). Therefore, we can infer that the non-conventional sources evaluated in our study (malanga and apple) are suitable for

obtaining resistant starch and that the greatest amount of resistant starch is obtained through the physical treatment of autoclaving compared to the chemical treatment of acid hydrolysis.

**Table 3.** Enzymatic determinations (%) of total starch (TS), available starch (AS), resistant starch (RS), and retrograde resistant starch (RRS) of native, autoclaved, and lintnerized corn, from apple, and malanga starches<sup>Ⓢ</sup>.

**Tabla 3.** Determinaciones enzimáticas (%) de almidón total (AT), almidón disponible (AD), almidón resistente (AR) y almidón resistente retrogradado (ARR) de almidones nativos, autoclaveados y lintnerizados de maíz, manzana y malanga<sup>Ⓢ</sup>.

Samples	TS	AS	RS	RRS
NCS	98.21 ± 0.26 <sup>a</sup>	95.15 ± 0.25 <sup>a</sup>	1.98 ± 0.03 <sup>b</sup>	0.80 ± 0.01 <sup>e</sup>
ACS	93.86 ± 0.32 <sup>b</sup>	84.37 ± 0.12 <sup>e</sup>	8.00 ± 0.05 <sup>c</sup>	1.10 ± 0.02 <sup>b</sup>
LCS	93.01 ± 0.09 <sup>bc</sup>	86.13 ± 0.04 <sup>c</sup>	5.69 ± 0.12 <sup>e</sup>	1.01 ± 0.01 <sup>c</sup>
NMS	91.13 ± 0.12 <sup>d</sup>	85.27 ± 0.05 <sup>d</sup>	3.24 ± 0.04 <sup>g</sup>	0.92 ± 0.01 <sup>d</sup>
AMS	89.33 ± 0.25 <sup>e</sup>	75.29 ± 0.11 <sup>g</sup>	14.45 ± 1.32 <sup>a</sup>	1.18 ± 0.01 <sup>a</sup>
LMS	88.04 ± 0.13 <sup>f</sup>	77.28 ± 0.07 <sup>f</sup>	9.27 ± 0.06 <sup>b</sup>	1.11 ± 0.01 <sup>b</sup>
NAS	93.56 ± 0.28 <sup>b</sup>	90.31 ± 0.15 <sup>b</sup>	2.17 ± 0.04 <sup>h</sup>	0.71 ± 0.01 <sup>f</sup>
AAS	92.36 ± 0.22 <sup>c</sup>	84.07 ± 0.04 <sup>e</sup>	7.28 ± 0.05 <sup>d</sup>	0.91 ± 0.01 <sup>d</sup>
LAS	90.96 ± 0.06 <sup>d</sup>	84.94 ± 0.04 <sup>d</sup>	4.85 ± 0.03 <sup>f</sup>	1.06 ± 0.01 <sup>bc</sup>

<sup>Ⓢ</sup>Mean of at least three repetitions ± standard error. Values with the same letter within columns are not significantly different according to Tukey's test ( $p > 0.05$ ).


### In vitro digestibility studies

Figure 1 shows the *in vitro* hydrolysis of native and modified corn, malanga, and apple starches. As can be seen, NCS presented the highest hydrolysis rate, in addition to a rapid increase in the percentage of starch hydrolysis (amylolysis) during the first 30 min and a subsequent decrease until reaching a value of  $\approx 58\%$ . In general, the hydrolysis values in all samples increased as the *in vitro* digestion time increased, which has been previously reported in cereal flours and starches such as oats (Kim and White, 2012; Zamudio-Flores *et al.*, 2015) and unconventional botanical sources such as the cowpea bean (*Vigna unguiculata*) (Ratnaningsih *et al.*, 2019). The hydrothermal modification by autoclave decreased the hydrolysis rate by  $\approx 41$ , 25, and 24% for corn, malanga, and apple, respectively, compared to their native counterparts; no statistically significant differences were observed ( $p \geq 0.05$ ) between the autoclaved starches from the different botanical sources. This type of behavior agrees with that reported by Ratnaningsih *et al.* (2019), who modified cowpea bean starch by applying successive autoclaving cycles, so these modified starches showed a lower rate of hydrolysis compared to native starch, which they associated with changes in the microstructure and increase in resistant starch obtained in the autoclaved samples.

In relation to the lintnerized samples, it was observed that the hydrochloric acid chemical treatment decreased the starch hydrolysis rate compared to the native starches in values of  $\approx 21$ , 5, and 3% for the corn, malanga, and apple samples, respectively; however, this reduction was lower than the values obtained in the samples subjected to hydrothermal treatment (autoclaved). The maximum rate of hydrolysis reached by the lintnerized starches was observed



in the 37 - 39% range. These values agree with those reported by Akanbi *et al.* (2019), who modified orange sweet potato starch by lintnerization, reporting a hydrolysis rate of  $\approx 35\%$ .

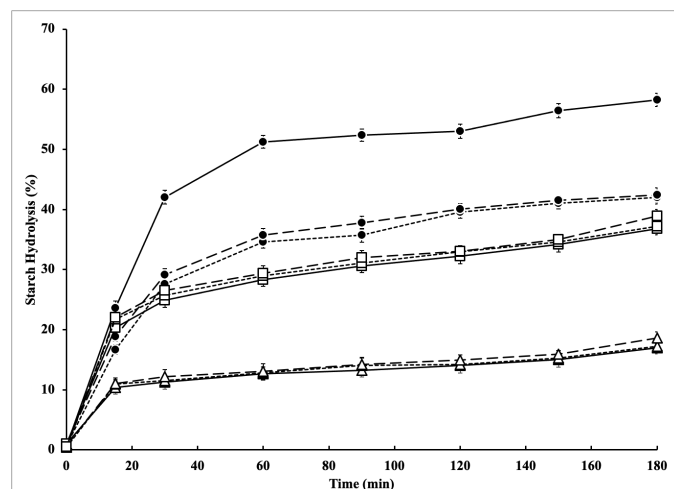

**Figure 1.** *In vitro* starch hydrolysis. Corn (—●—), malanga (---●---), manzana (—■—), circles (native starches), triangles (autoclaved starches), squares (lintnerized starches). Values represent the mean of at least three replicates ( $n > 3$ ). Bars represent the standard error of the mean.

**Figura 1.** Hidrólisis de almidón *in vitro*. Maíz (—●—), malanga (---●---), manzana (—■—), círculos (almidones nativos), triángulos (almidones autoclaveados), cuadrados (almidones lintnerizados). Los valores representan la media de al menos tres réplicas ( $n > 3$ ). Las barras representan el error estándar de la media.

## CONCLUSIONS

Resistant starches type 3 (RS3) and 4 (RS4) were obtained by the application of successive cycles of autoclaving/cooling and lintnerization (acid hydrolysis), respectively, from native starches of corn (NCS), apple (NAS), and malanga (NMS). When comparing all analyzed samples, AMS had the highest RS content (14%), and NCS the lowest (1.98%). Furthermore, the autoclaved treatment decreased the enzymatic hydrolysis rate by  $\approx 24 - 41\%$  compared to native starches, while with the lintnerization treatment, this reduction was smaller ( $\approx 3 - 21\%$ ). Regarding the physicochemical properties, the autoclaved and lintnerized treatments reduced the apparent amylose content by  $\approx 5\%$ , producing amylose with lower molecular weight ( $\approx 80 - 86$  kDa) for autoclaved starches and  $\approx 92 - 101$  kDa for lintnerized starches. At the same time, the luminosity decreased by the autoclaved treatment and not by the lintnerization process. Therefore, AMS could be used in bakery applications (added in cookies or pasta) where it is desired to increase the RS content without affecting the color sensory characteristics.

## ACKNOWLEDGES

The first author (VAM) thanks the "National Council of Science and Technology" (CONACYT-Mexico) for the scholarship granted to carry out his studies in the Master of Science Program at CIAD-Cuauhtemoc Unit, Chihuahua, Mexico. The authors are grateful for the support of SAGARPA-CONACYT-

Mexico for financing the project entitled: "Development of technologies for the use and exploitation of malanga corms (*Xanthosoma saggitifolium*) from the state of Chiapas and Veracruz", with code 2016-01-277457. The technical supports from engineers Arturo Ramos Martinez, Adrian Gomez Ornelas and Irma Graciela Flores Cortes are also appreciated. This study is a product of the Research Group (GI) of Carbohydrates, Packaging and Functional Foods (CEAF) of CIAD-Cuauhtemoc, Chihuahua, Mexico, led by Dr. Paul Baruk Zamudio Flores.

## REFERENCES

- Abioye, V.F., Adeyemi, I.A., Akinwande, B.A., Kulakow, P. and Maziya-Dixon, B. 2017. Effect of steam cooking and storage time on the formation of resistant starch and functional properties of cassava starch. *Cogent Food and Agriculture*. 3(1): 1296401.
- Aboubakar, N.Y., Scher, J. and Mbofung, C.M.F. 2008. Physicochemical, thermal properties and microstructure of six varieties of taro (*Colocasia esculenta* L. Schott) flours and starches. *Journal of Food Engineering*. 86(2): 294-305.
- Akanbi, C.T., Kadiri, O. and Gbadamosi, S.O. 2019. Kinetics of starch digestion in native and modified sweetpotato starches from an orange fleshed cultivar. *International Journal of Biological Macromolecules*. 134: 946-953.
- AOAC. 2002. Official Methods of Analysis of the Association of Official Analytical Chemists. Association of Official Analytical Chemist, Gaithersburg, MA, EUA.
- Aparicio-Saguilán, A., Flores-Huicochea, E., Tovar, J., García-Suárez, F., Gutiérrez-Meraz, F. and Bello-Pérez, L.A. 2005. Resistant starch-rich powders prepared by autoclaving of native and lintnerized banana starch: Partial characterization. *Starch/Stärke*. 57(9): 405-412.
- Ashwar, B.A., Gani, A., Shah, A. and Masoodi, F.A. 2017. Physicochemical properties, *in-vitro* digestibility and structural elucidation of RS4 from rice starch. *International Journal of Biological Macromolecules*. 105: 471-477.
- Ashwar, B.A., Gani, A., Shah, A., Wani, I.A. and Masoodi, F.A. 2016a. Preparation, health benefits and applications of resistant starch—A review. *Starch-Stärke*. 68(3-4): 287-301.
- Ashwar, B.A., Gani, A., Wani, I.A., Shah, A., Masoodi, F.A. and Saxena, D.C. 2016b. Production of resistant starch from rice by dual autoclaving-retrogradation treatment: *In vitro* digestibility, thermal and structural characterization. *Food Hydrocolloids*. 56: 108-117.
- Ashwar, B.A., Gani, A., Wani, I.A., Shah, A., Masoodi, F.A. and Saxena, D.C. 2016c. Production of resistant starch from rice by dual autoclaving-retrogradation treatment: *In vitro* digestibility, thermal and structural characterization. *Food Hydrocolloids*. 56: 108-117.
- Babu, A.S., Mahalakshmi, M. and Parimalavalli, R. 2014. Comparative study on properties of banana flour, starch and autoclaved starch. *Trends in Carbohydrate Research*. 6(1): 38-44.
- Berry, C.S. 1986. Resistant starch: formation and measurement of starch that survives exhaustive digestion with amyolytic enzymes during the determination of dietary fiber. *Journal of Cereal Science*. 4(4): 301-314.
- Bustillos-Rodríguez, J.C., Ordóñez-García, M., Tirado-Gallagos, J.M., Zamudio-Flores, P.B., Ornelas-Paz, J. de J., Acosta-Muñiz,

- C.H., Gallegos-Morales, G., Sepúlveda-Ahumada, D.R., Salas-Marina, M.A., Berlanga-Reyes, D.I., Aparicio-Saguilán, A. and Rios-Velasco, C. 2019. Physicochemical, thermal and rheological properties of native and oxidized starch from corn landraces and hybrids. *Food Biophysics*. 14: 182-192.
- Bustillos-Rodríguez, J.C., Tirado-Gallegos, J.M., Ordoñez-García, M., Zamudio-Flores, P.B., Ornelas-Paz, J. de J., Acosta-Muñiz, C.H. and Rios-Velasco, C. 2018. Physicochemical, thermal and rheological properties of three native corn starches. *Food Science and Technology*. 39(1): 149-157.
- Cai, C., Wei, B., Tian, Y., Ma, R., Chen, L., Qiu, L. and Jin, Z. 2019. Structural changes of chemically modified rice starch by one-step reactive extrusion. *Food Chemistry*. 288: 354-360.
- Chiu, C. and Solarek, D. 2009. Modification of Starches. In: BeMiller, J. and Whistler, R. (Eds.).
- Dai, L., Qiu, C., Xiong, L. and Sun, Q. 2015. Characterisation of corn starch-based films reinforced with taro starch nanoparticles. *Food Chemistry*. 174: 82-88.
- Deka, D. and Sit, N. 2016. Dual modification of taro starch by microwave and other heat moisture treatments. *International Journal of Biological Macromolecules*. 92: 416-422.
- Englyst, H.N., Kingman, S.M. and Cummings, J.H. 1992. Classification and measurement of nutritionally important starch fractions. *European Journal of Clinical Nutrition*. 46: S33-50.
- Espinosa-Solis, V., Zamudio-Flores, P.B., Espino-Díaz, M., Vela-Gutiérrez, G., Rendón-Villalobos, J.R., Hernández-González, M., Hernández-Centeno, F., López-De la Peña, H.Y., Salgado-Delgado, R., and Ortega-Ortega, A. 2021. Physicochemical characterization of resistant starch type-III (RS3) obtained by autoclaving malanga (*Xanthosoma sagittifolium*) flour and corn starch. *Molecules*. 26: 4006.
- Fox, E., Shotton, K. and Ulrich, C. 1995. Sigma-Stat: Manual del usuario, versión 2.1 para Windows 95 NT y 3.1. Editorial Jandel Scientific Co., EUA.
- Franco, C.M., Cabral, R.A. and Tavares, D.Q. 2002. Structural and physicochemical characteristics of lintnerized native and sour cassava starches. *Starch-Stärke*. 54(10): 469-475.
- Fuentes-Zaragoza, E., Riquelme-Navarrete, M.J., Sánchez-Zapata, E. and Pérez-Álvarez, J.A. 2010. Resistant starch as functional ingredient: A review. *Food Research International*. 43(4): 931-942.
- Gani, A., Jan, A., Shah, A., Masoodi, F.A., Ahmad, M., Ashwar, B.A. and Wani, I.A. 2016. Physico-chemical, functional and structural properties of RS3/RS4 from kidney bean (*Phaseolus vulgaris*) cultivars. *International Journal of Biological Macromolecules*. 87: 514-521.
- García-Tejeda, Y.V., Zamudio-Flores, P.B., Bello-Pérez, L.A., Romero-Bastida, C.A. and Solorza-Feria, J. 2011. Oxidación del almidón nativo de plátano para su uso potencial en la fabricación de materiales de empaque biodegradables: Caracterización física, química, térmica y morfológica. *Revista Iberoamericana de Polímeros*. 12(3): 125-135.
- Goñi, I., García-Alonso, A. and Saura-Calixto, F. 1997. A starch hydrolysis procedure to estimate glycemic index. *Nutritional Research*. 17: 427-437.
- Goñi, I., García-Díaz, L., Mañas, E. and Saura-Calixto, F. 1996. Analysis of resistant starch: A method for foods and food products. *Food Chemistry*. 56(4): 445-449.
- Holm, J., Hagander, B., Björck, I., Eliasson, A.C. and Lundquist, I. 1989. The effect of various thermal processes on the glycemic response to whole grain wheat products in humans and rats. *The Journal of Nutrition*. 119(11): 1631-1638.
- Jan, K.N., Panesar, P.S. and Singh, S. 2017. Process standardization for isolation of quinoa starch and its characterization in comparison with other starches. *Journal of Food Measurement and Characterization*. 11(4): 1919-1927.
- Jane, J-L., Chen, M., Lee, L., McPherson, A., Wong, K-S., Radosavljevic, M. and Kasemsuwan, T. 1999. Effects of amylopectin branch chain length and amylose content on the gelatinization and pasting properties of starch. *Cereal Chemistry*. 76(5): 629-637.
- Juarez-Enriquez, E., Olivas, G.I., Ortega-Rivas, E., Zamudio-Flores, P.B., Perez-Vega, S., Sepulveda, D.R. 2019. Water activity, not moisture content, explains the influence of water on powder flowability. *LWT*. 100: 35-39,
- Kim, H.J. and White, P.J. 2012. *In vitro* digestion rate and estimated glycemic index of oat flours from typical and high  $\beta$ -glucan oat lines. *Journal of Agricultural and Food Chemistry*. 60: 5237-5242.
- Kringel, D.H., Dias, A.R.G., Zavareze, E.D.R. and Gandra, E.A. 2020. Fruit wastes as promising sources of starch: Extraction, properties, and applications. *Starch-Stärke*. 72(3-4): 1900200.
- Kwon, C., Kim, H.R., Moon, T.W., Lee, S.H. and Lee, C.J. 2019. Structural and physicochemical characteristics of granular malic acid-treated sweet potato starch containing heat-stable resistant starch. *Journal of Chemistry*. 2903252: 10.
- Lawal, O.S. 2004. Composition, physicochemical properties and retrogradation characteristics of native, oxidised, acetylated and acid-thinned new cocoyam (*Xanthosoma sagittifolium*) starch. *Food Chemistry*. 87(2): 205-218.
- Li, H., Gidley, M.J. and Dhital, S. 2019. Almidones de alto contenido de amilosa para cerrar la "brecha de la fibra": Desarrollo, estructura y funcionalidad nutricional. Revisión completa en Ciencia de Alimentos e Inocuidad de Alimentos. 18(2): 362-379.
- Li, L., Yuan, T.Z. and Ai, Y. 2020. Development, structure and *in vitro* digestibility of type 3 resistant starch from acid-thinned and debranched pea and normal maize starches. *Food Chemistry*. 126485.
- Ma, Z. and Boye, J.I. 2018. Research advances on structural characterization of resistant starch and its structure-physiological function relationship: A review. *Critical Reviews in Food Science and Nutrition*. 58(7): 1059-1083.
- Neder-Suárez, D., Amaya-Guerra, C.A., Báez-González, J.G., Quintero-Ramos, A., Aguilar-Palazuelos, E., Galicia-García, T., Ramírez-Wong, B., Campos-Venegas, K. and Zazueta-Morales, J. de J. 2018. Resistant starch formation from corn starch by combining acid hydrolysis with extrusion cooking and hydrothermal storage. *Starch-Stärke*. 70(5-6): 1700118.
- Obadi, M., Li, C., Li, Q., Li, X., Qi, Y. and Xu, B. 2020. Relationship between starch fine structures and cooked wheat starch digestibility. *Journal of Cereal Science*. 95: 103047.
- Ojinnaka, M.C., Akobundu, E.N.T. and Iwe, M.O. 2009. Cocoyam starch modification effects on functional, sensory and cookies qualities. *Pakistan Journal of Nutrition*. 8(5): 558-567.
- Ozturk, S., Koxsel, H. and Ng, P.K. 2011. Production of resistant starch from acid-modified amylopectin starches with enhanced functional properties. *Journal of Food Engineering*. 103(2): 156-164.

- Punia, S., Siroha, A.K., Sandhu, K.S. and Kaur, M. 2019. Rheological behavior of wheat starch and barley resistant starch (type IV) blends and their starch noodles making potential. *International Journal of Biological Macromolecules*. 130: 595-604.
- Radley, J.A. 1976. *Starch production technology*. London: Applied Science Publishers Ltd. 214 p.
- Ratnaningsih, N., Harmayani, E., and Marsono, Y. 2019. Physicochemical properties, *in vitro* starch digestibility, and estimated glycemic index of resistant starch from cowpea (*Vigna unguiculata*) starch by autoclaving-cooling cycles. *International Journal of Biological Macromolecules*. 1-40.
- Raungrusmee, S. and Anal, A.K. 2019. Effects of lintnerization, autoclaving, and freeze-thaw treatments on resistant starch formation and functional properties of pathumthani 80 rice starch. *Foods*. 8(11): 558.
- Regand, A., Chowdhury, Z., Tosh, S.M., Wolever, T.M.S. and Wood, P. 2011. The molecular weight, solubility and viscosity of oat beta-glucan affect human glycemic response by modifying starch digestibility. *Food Chemistry*. 129: 297-304.
- Rivas-González, M., Méndez-Montealvo, M.G.C., Sánchez-Rivera, M.M., Núñez-Santiago, M.C. and Bello-Pérez, L.A. 2008. Morphological molecular and physicochemical characterization of oxidized and lintnerized banana starch. *Agrociencia*. 42(5): 487-497.
- Saura-Calixto, F., Goñi, I., Bravo, L. and Mañas, E. 1993. Resistant starch in foods: Modified method for dietary fiber residues. *Journal of Food Science*. 58(3): 642-643.
- Shah, A., Masoodi, F.A., Gani, A. and Ashwar, B.A. 2016. *In-vitro* digestibility, rheology, structure, and functionality of RS3 from oat starch. *Food Chemistry*. 212: 749-758.
- Shi, M., Wang, K., Yu, S., Gilbert, R.G. and Gao, Q. 2016. Structural characterizations and *in vitro* digestibility of acid-treated wrinkled and smooth pea starch (*Pisum sativum* L.). *Starch-Stärke*. 68(7-8): 762-770.
- Simsek, S. and El, S.N. 2012. Production of resistant starch from taro (*Colocasia esculenta* L. Schott) corm and determination of its effects on health by *in vitro* methods. *Carbohydrate Polymers*. 90(3): 1204-1209.
- Stevenson, D.G., Domoto, P.A. and Jane, J.L. 2006. Structures and functional properties of apple (*Malus domestica* Borkh) fruit starch. *Carbohydrate Polymers*. 63(3): 432-441.
- Tirado-Gallegos, J.M., Zamudio-Flores, P.B., Ornelas-Paz, J. de J., Rios-Velasco, C., Acosta-Muñiz, C.H., Gutiérrez-Meraz, F., Islas-Hernández, J.J. and Salgado-Delgado, R. 2016. Efecto del método de aislamiento y el estado de madurez en las propiedades fisicoquímicas, estructurales y reológicas de almidón de manzana. *Revista Mexicana de Ingeniería Química*. 15(2): 391-408.
- Torruco-Uco, J.G., Chávez-Murillo, C.E., Hernández-Centeno, F., Salgado-Delgado, R., Tirado-Gallegos, J.M. and Zamudio-Flores, P.B. 2016. Use of high-performance size-exclusion chromatography for characterization of amylose isolated from diverse botanical sources. *International Journal of Food Properties*. 19(6): 1362-1369.
- Van Hung, P., Vien, N.L. and Phi, N.T.L. 2016. Resistant starch improvement of rice starches under a combination of acid and heat-moisture treatments. *Food Chemistry*. 191: 67-73.
- Vargas, G., Martínez, P. and Velezmoro, C. 2016. Propiedades funcionales de almidón de papa (*Solanum tuberosum*) y su modificación química por acetilación. *Scientia Agropecuaria*. 7: 223-230.
- Walpole, E.R., Myers, H.R. and Myers, L.S. 1999. *Probabilidad y estadística para ingenieros*. Prentice-Hall Hispanoamericana, S.A., México.
- Wang, L. and Wang, Y.J. 2001. Structures and physicochemical properties of acid-thinned corn, potato and rice starches. *Starch-Stärke*. 53(11): 570-576.
- Waterschoot, J., Gomand, S.V., Fierens, E. and Delcour, J.A. 2015. Production, structure, physicochemical and functional properties of maize, cassava, wheat, potato and rice starches. *Starch/Stärke*. 67(1-2): 14-29.
- Whale, S.K. and Singh, Z. 2007. Endogenous ethylene and color development in the skin of 'Pink Lady' apple. *Journal of the American Society for Horticultural Science*. 132(1): 20-28.
- Xia, H., Li, B.Z. and Gao, Q. 2017. Effect of molecular weight of starch on the properties of cassava starch microspheres prepared in aqueous two-phase system. *Carbohydrate Polymers*. 177: 334-340.
- Zamudio-Flores, P.B., Tirado-Gallegos, J.M., Monter-Mirando, J.G., Aparicio-Saguilán, A., Torruco-Uco, J.G., Salgado-Delgado, R. and Bello-Pérez, L.A. 2015. *In vitro* digestibility and thermal, morphological and functional properties of flours and oat starches of different varieties. *Revista Mexicana de Ingeniería Química*, 14(1): 81-97.
- Zeng, S., Wu, X., Lin, S., Zeng, H., Lu, X., Zhang, Y. and Zheng, B. 2015. Structural characteristics and physicochemical properties of lotus seed resistant starch prepared by different methods. *Food Chemistry*. 186: 213-222.